



ISSN: 2350-0328

**International Journal of Advanced Research in Science,
Engineering and Technology**

Vol. 3, Issue 3 , March 2016

Optimization of Process Parameter of CNC Abrasive Water Jet Machine For Titanium Ti 6Al 4V material

MayurM.Mhamunkar,NiyatiRaut

P.G. Student, Department of Mechanical Engineering, Viva college of Engineering & Technology ,Virar, Maharashtra, India

Lecturer, Department of Mechanical Engineering, Viva college of Engineering & Technology, Virar, Maharashtra, India

ABSTRACT: Abrasive water jet machining is one of the most non-conventional methods for machining. It is widely used in fabrication industry to machine the materials like aluminum, mild steel, copper, glass, titanium, hard rock material, graphite, ceramics, composite material, etc. Abrasive Water Jet Machining (AWJM) of Titanium (Ti 6Al 4V) has commercial importance due to its decent machining characteristics. In the present paper an effort has been made to optimize machining factors employed in Abrasive Jet Machining of Ti 6Al 4V using Taguchi technique. The methodology used is established on the analysis of variance and Grey Relation Analysis (GRA) to optimize the AWJM process factors for effective Material Removal Rate (MRR) and Surface Roughness (SR). Significant AWJM machining parameters such as traverse speed, abrasive flow rate & stand-off Distance were expected for optimized MRR and SR. It was set that determined optimal combination of AWJM process factors satisfy the actual need for Ti 6Al 4V in actual run-through.

KEYWORDS: Abrasive Water Jet Machine (AWJM), Grey Relation Analysis (GRA), ANOVA, MRR, SR

I. INTRODUCTION

Among Titanium based alloys specifically Ti 6Al 4V has decent mechanical properties like great corrosion resistance the high strength, low weight ratio. It has good ability to resist oxidation. It is used in aircraft turbine engine components, aerospace, high-performance automotive parts, aircraft structural components, medical devices, marine applications, and sports kit. The alloy has great strength it cannot be machined by using the traditional methods as of its work hardening nature. Hence non-traditional techniques like laser machining and abrasive water jet machining etc. are used. Laser Cutting is normally economical for cutting Ti 6Al 4V sheets up to 2mm thick and beyond 2mm thick abrasive water jet machining is frequently used. On the other hand, AJWM is favored over laser cutting because of its capability to machine the components with minimum slot width. Abrasive water jet machining of grey cast iron, aluminum, mild steel and hard polymers and composites has been studied comprehensively for optimized material removal rate (MRR) and surface roughness (SR) using GRA method. Nozzle traverse speed and water pressure are major manipulating factors in case of MRR while abrasive mass flow rate and pressure intensely influences SR. Other factors such as standoff distance, abrasive grain size are sub-significant in influencing MRR or SR. It was illustrious that ferrous materials need expressively high abrasive flow rate compared to non-ferrous materials whereas composites and tough polymers can be machined through moderate abrasive flow rates. Abrasive jet water machining of Ti 6Al 4V was prevailing optimization of machining parameters did not receive much consideration. Hence in the existing work an effort has been made to optimize the cutting parameters in the AWJM of Ti 6Al 4V alloy using GRA method. Nozzle transverse speed, abrasive flow rate and standoff distance were optimized for surface roughness (SR) and material removable rate (MRR). Analysis of variance (ANOVA) and Gray relation analysis were used for optimization of machining parameters.

**II. Experimental details****A. Work piece material**

Here work piece Titanium Ti 6Al 4V is having hardness of 33 HRC for the experiment. The Length and breadth of work piece was 120 mm and thickness of plate 16 mm. Ti 6Al 4V is a high strength alloy, which is used in a diversity of mechanical applications. Mechanical properties of this material are elastic modulus 120-130Gpa, density $4.42 \times 10^3 \text{ g/mm}^3$, tensile strength 860 MPa, yield strength 758MPa.

B. Abrasive Material

Aluminum oxide consists of blunt shaped grains and is very hard in its lowest polished form. It is manufactured in variety of refinements and by its flexibility can be used to very hard to soft use, making it the very frequently used abrasive. The abrasive water jet machining apparatus used consists of a high pressure pump SL-V 50 Plus made by KMT that is built on a CNC AWJM cutting portal with an abrasive feeding arrangement that varies the feed rate in the range of 100 – 900 grams /min. 80Mesh Garnet sand was castoff as Abrasive material, the values of abrasive particles granulation varies in the middle of 160 - 310 μm with a density of 2300 kg/m³.

C. Nozzle

Cutting head consists of orifice, mixing chamber and focusing tube (Nozzle) or insert where water jet is formed and mixed with abrasive particles to form abrasive water jet. The orifice used had an inner diameter of 0.25 mm and the nozzle inner diameter was 0.75mm. Water passed through the pipes is carried to the jet or cutting head. The standoff distance between the mixing tube and the material is typically 0.5 mm to 2.5 mm. more standoff (greater than 3 mm) can cause a frosting to appear at top of the cut edge of the material. Various Water jet systems reduce or reduce this frosting by cutting below water or using other methods.

D. Measurement of surface roughness and material removal rate

The surface roughness of the trials was measured with Mitutoyo make Surface roughness tester and the material removal rate measured by the calculation.

E. Design of experiment

In this study, four controllable variables, explicitly, traverse speed, Abrasive flow rate, and Standoff distance. In the machining factor design, three levels of the cutting parameters were carefully chosen, shown in Table 1.

Table 1. Process parameters with their levels.

Sr.No.	Process Parameter	Unit	Level-1	Level-2	Level-3
1	Traverse Speed(T)	Mm/min	30	55	80
2	Abrasive flow rate(F)	grams/min	200	250	300
3	Stand of distance(S)	mm	1	1.5	2

By table 1, L9 orthogonal array of “Taguchi method” has been carefully chosen for the experiments in MINITAB 15. 9 experiments will carried out with abrasives. SR and MRR have been selected as response variables. All these data are used for the study and evaluation of the optimal parameters combination. Experiment result as shown in Table2.

Table 2.Experiment Result

EX.NO	T	F	S	MRR (gm/min)	Ra (µm)
1	30	200	1	1.611	3.2632
2	30	250	1.5	1.758	2.9456
3	30	300	2	1.827	2.4786
4	55	200	1.5	2.601	4.0023
5	55	250	2	2.862	4.1896
6	55	300	1	2.781	3.1270
7	80	200	2	3.666	3.6713
8	80	250	1	3.735	3.3293
9	80	300	1.5	3.843	4.1636

III. METHODOLOGY

A. Grey relational analysis method

In Grey relational analysis, trial results were first normalized and then the grey relational coefficient (GRC) was calculated from the normalized experimental data to definite the relationship between the desired and actual experimental records. Then, the grey relational grade (GRG) was calculated by averaging the grey relational coefficient corresponding to every process response. The overall assessment of the multiple process responses is grounded on the grey relational grade (GRG).

B. Data preprocessing

In S/N ratio method this formula was used for MRR and SR

$$L_{HB} = \frac{1}{n} \sum_{i=1}^n \frac{1}{y_{MRR}^2} \dots\dots\dots (1)$$

$$L_{LB} = \frac{1}{n} \sum_{i=1}^n y_{SR}^2 \dots\dots\dots (2)$$

In grey relational generation, the normalized data corresponding to Lower-the-Better (LB) criterion can be expressed as:

$$x_i(k) = \frac{\max y_i(k) - y_i(k)}{\max y_i(k) - \min y_i(k)} \dots\dots\dots (1)$$

For Higher-the-Better (HB) criterion, the normalized data can be stated as:

$$x_i(k) = \frac{y_i - \min y_i(k)}{\max y_i(k) - \min y_i(k)} \dots\dots\dots (2)$$

Where $x_i(k)$ is the value after the grey relational generation, $\min y_i(k)$ is the smallest value of $y_i(k)$ for the k_{th} response, and $\max y_i(k)$ is the major value of $y_i(k)$ for the k_{th} response.

An ideal sequence is $x_0(k)$ ($k=1, 2$) for dual responses. The definition of the grey relational grade in the grey relational Analysis is to indicate the relational degree among the nine sequences $x_0(k)$ and $x_i(k)$, $i=1, 2, \dots, 27$; $k=1, 2$). The grey relational coefficient $\xi_i(k)$ can be calculated as:

$$\xi_i(k) = \frac{\Delta_{min} + \theta \Delta_{max}}{\Delta_{0i}(k) + \theta \Delta_{max}} \dots\dots\dots (3)$$

Where $\Delta_i = |X_0(k) - X_i(k)|$ = difference of the exact value $x_0(k)$ and $x_i(k)$; θ is the distinguishing coefficient $0 \leq \theta \leq 1$; $\min \Delta = \forall j \min_i \Delta_{0i} = \Delta_{0j_{min}}$ = the lowest value of Δ_{0i} ; and $\max \Delta = \forall j \max_i \Delta_{0i} = \Delta_{0j_{max}}$ = largest value of Δ_{0i} . Later averaging the grey relational coefficients, the grey relational grade γ_i can be computed as

$$\gamma_i = \frac{1}{n} \sum_{k=1}^n \xi_i(k) \dots\dots\dots(4)$$

Where n = number of process responses. The higher value of grey relational grade corresponds to strong relational degree between the reference sequence x0 (k) and the set sequence xi (k). The reference sequence x0 (k) signifies the best process sequence. Therefore, higher grey relational grade means that the corresponding factor combination is nearer to the optimal.

IV. PRESENTATION AND ANALYSIS OF RESULTS

A level average analysis was accepted to deduce the results. This analysis is based on merging the data associated with each level for each parameter. The variance in the average results for the highest and lowest average response is the measure of the influence of that parameter. The highest value of this variance is related to the largest effects of that particular factor. Data pre-processing of each performance characteristic and the trial results for the grey relational conferring to formulas (1),(2),(3) and (4) are given in Table 3 and 4,5 and 6.

Table 3. Signal-to-Noise Ratio

Response Values		S/N Ratio	
MRR(gm/min)	Ra(µm)	MRR(dB)	Ra(dB)
1.611	3.2632	4.141911	-10.2729
1.758	2.9456	4.900377	-9.38348
1.827	2.4786	5.234771	-7.88413
2.601	4.0023	8.302807	-12.0462
2.862	4.1896	9.133393	-12.4435
2.781	3.1270	8.88402	-9.90256
3.666	3.6713	11.28385	-11.2964
3.735	3.3293	11.44581	-10.4471
3.843	4.1636	11.69341	-12.3894

TABLE 4 NORMALIZE VALUE OF SR, AND MRR

Expt. No	Normalized S/N Ratio	
	MRR	Ra
1	0.0000	0.5239
2	0.1004	0.3288
3	0.1447	0.0000
4	0.5510	0.9129
5	0.6610	1.0000
6	0.6280	0.4427
7	0.9458	0.7484

8	0.9672	0.5621
9	1.0000	0.9881


Table.5 :Deviation sequence and grey relational coefficient and Grey relation grade

Expt. No	Deviation Sequence		Grey Relational Coefficient		Gray relation Grade
	MRR	Ra	MRR	Ra	0.4227931
1	1.0000	0.4761	0.3333	0.5123	0.3920927
2	0.8996	0.6712	0.3573	0.4269	0.3511305
3	0.8553	1.0000	0.3689	0.3333	0.6892282
4	0.4490	0.0871	0.5269	0.8516	0.7979603
5	0.3390	0.0000	0.5959	1.0000	0.5231382
6	0.3720	0.5573	0.5734	0.4729	0.7836988
7	0.0542	0.2516	0.9021	0.6653	0.7357895
8	0.0328	0.4379	0.9385	0.5331	0.9884049
9	0.0000	0.0119	1.0000	0.9768	0.4227931

Table.6: The Main Effects of the Factors on the Grey Relational Grade

Symbols	parameters	Grey Relational Grade			Main effect	Rank
		Level-1	Level-2	Level-3		
A	Traverse Speed (T)	0.3887	0.670109	0.835964	0.4473	1
B	Abrasive flow rate (F)	0.631907	0.641947	0.620891	0.021056	3
C	Stand of distance(S)	0.560574	0.689909	0.644263	0.129335	2

In grey relational analysis greater the grey relational grade of experiment states that the corresponding experimental combination is optimum situation for multi objective optimization and gives enhanced product quality. Form the basis of the GRG, the factor influence can be estimated and the optimal level for each governable factor can also be determined. From the Table 5 It is found that experiment 8 has the best multiple performance characteristic among 9 experiments, because it has the highest grey relational grade of 0.9884 The main effects plot of grey relational grade vs. process parameter can produced by Minitab 15 statistical software to find out optimum parameter combination, is shown in graph 1.

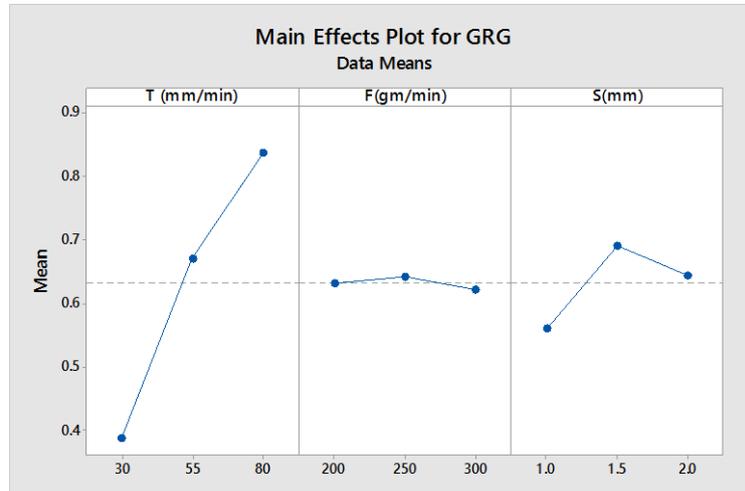

Graph 1.Mean effect plot of GRG Vs T,F,S

From the graph 1.and table no. 6 It is conclude that the optimum condition for surface roughness is meeting at Traverse speed(A1), Abrasive flow rate (B2),standoff distance (C2).then by using this data the predicted MRR and SR were found out by Minitab software 3.7571gm/min and 3.8788µm respectively

V. CONCLUSION/RECOMMENDAIONS

The confirmation experiments were performed with the optimum combination of the machining parameters obtained from GRA Technique. The mentioned parametric combination for optimum material removal rate is T3F2S2 and after confirmation test the optimum response value of MRR is 3.9420 grams/min. The confirmation experiments were performed on Surface roughness with T3F2S2 levels as obtained from GRA Technique. The optimal response valuefor Surface roughness after confirmation test is 3.6911µm. These test results offers us a greater feature in decide on significant parameters on output parameters such as MRR, SR while machining Titanium Ti 6Al 4V material on abrasive water jet machining.

REFERENCES

- [1] LeeladharNagdeve, VedanshChaturvedi, JyotiVimal, "Implementation of Taguchi approach for optimization of abrasive water jet machining process parameters", International Journal of Instrumentation, Control and Automation (IJICA) ISSN: 2231-1890, Vol-1 Iss-3,4. Pages 9 to 13, (2012)
- [2] AzlanMohdZaina,, HabibollahHaronb, Safian Sharif "Optimization of process parameters in the abrasive waterjet machining using integrated SA-GA Applied Soft Computing" ,11, (2011) 5350-5359
- [3]Mehul.A.Raval, Chirag. P. Patel"Parametric Optimization of Magnetic Abrasive Water Jet Machining of AISI 52100 Steel Using Grey Relational Analysis" / International Journal of Engineering Research and Applications (IJERA) ISSN: 2248-9622 www.ijera.com Vol. 3, Issue 4, pp. 527-530, May-Jun (2013)
- [4]M.SreenivasaRao, S.RavinderB and A. Seshu Kumar "Parametric Optimization of Abrasive Waterjet Machining for Mild Steel Taguchi Approach" International Journal of Current Engineering and Technology, Special Issue-2 (Feb 2014)
- [5]P. P. Badgujar, M. G. Rathi, "Taguchi Method Implementation in Abrasive Waterjet Machining Process Optimization",International Journal of Engineering and Advanced Technology (IJEAT) ISSN: 2249 – 8958, Volume-3, Issue-5, June2014
- [6]ZoranJurkovic, MladenPerinic, Sven Maricic,MilenkoSekulic,VesnaMandic, "Application Of Modelling And Optimization Methods In Abrasive Water Jet Machining", Journal Of Trends In The Development Of Machinery And Associated Technology Vol. 16, No. 1, Issn 2303-4009 (Online), P.P. 59-62, , 2012
- [7]D. Sidda Reddy, A. Seshu Kumar, M.SreenivasaRao, "Parametric Optimization of Abrasive Water Jet Machining of Inconel 800H Using Taguchi Methodology", Universal Journal of Mechanical Engineering 2(5): 158-162, 2014
- [8] M. ChithiraiPonSelvan, N. MohanaSundaraRaju, H. K. Sachidananda "Effects Of Process Parameters On Surface Roughness In Abrasive Waterjet Cutting Of AluminiumFront". Mech. Eng., 7(4): 439-444, 2012,Doi 10.1007/S11465-012-0337-0
- [9]Mayur C. Pate, Mr. S. B. Patel, Mr. R.H. Patel, "Parametric Analysis Of Abrasive Water Jet Machining Of Aluminium 6351 T6"International Journal For Technological Research In Engineering Volume 1, Issue 12, August-2014
- [10]Vinod B. Patel, Prof. V. A. Patel, "Parametric analysis of Abrasives water jet machining of EN8 Material", International Journal of Engineering Research and Applications (IJERA)ISSN: 2248-9622 www.ijera.com Vol. 2, Issue 3, pp.3029-3032, , May-Jun 2012



ISSN: 2350-0328

International Journal of Advanced Research in Science, Engineering and Technology

Vol. 3, Issue 3, March 2016

- [11] M. A. Azmir¹, A.K. Ahsan, A. Rahmah, M.M. Noor And A.A. Aziz “Optimization Of Abrasive Waterjet Machining Process Parameters Using Orthogonal Array With Grey Relational Analysis Regional Conference On Engineering Mathematics, Mechanics, Manufacturing & Architecture (Em3arc), Pp 21~30, 2007
- [12] Y.B Gaidhani, V.S.Kalamani, “Abrasive water jet review and parameter selection by AHP method”, IOSR Journal of Mechanical and Civil Engineering (IOSR-JMCE) e-ISSN: 2278-1684,p-ISSN: 2320-334X, Volume 8, Issue 5, PP 01-06, (Sep. - Oct. 2013)
- [13]Preeti, Dr. Rajesh Khanna, Rahul Dev Gupta³, Vishal Gupta⁴Measuring, “Material Removal Rate of Marble by Using Abrasive Water Jet Machining”, IOSR Journal of Mechanical and Civil Engineering (IOSR-JMCE) e-ISSN: 2278-1684, p-ISSN: 2320-334X. PP 45-49,2013
- [14]Kapil Kumar Chauhan,Dinesh Kumar Chauhan, “Optimization of Machining Parameters of Titanium Alloy for Tool Life”,Journal of Engineering, Computers & Applied Sciences (JEC&AS) ISSN No: 2319-5606
Volume 2, No.6, June 2013
- [15] J. Laxman, Dr. K. Guru Raj, “Optimization of EDM Process Parameters on Titanium Super Alloys Basedon the Grey Relational Analysis”, International Journal of Engineering Research ISSN:2319-6890(online),2347-5013(print)Volume No.3, Issue No.5, pp : 344-348 01 May 2014.

Authors Biography



Designation: Lecturer of Mechanical Engineering Department At Thakur college of engineering and Technology, Kandivali, Dist:Mumbai, Maharashtra
Qualification: BE Mechanical, Pursuing ME in Manufacturing System Engineering
Experience: 3 yrs
Research Interests: Manufacturing Systems and Automation



Designation: HOD Mechanical Engineering Department At Viva college of engineering and Technology, Virar, Dist:palghar, Maharashtra
Qualification: ME Thermal
Experience: 8 yrs
Research Interests: Applied Thermodynamics, Heat transfer